

EUROPEAN TECHNICAL ASSESSMENT

BZ-S



 **Scell-it[®]** 

Centre Scientifique et
Technique du Bâtiment

84 avenue Jean Jaurès
CHAMPS-SUR-MARNE
F-77447 Marne-la-Vallée Cedex 2

Tél. : (33) 01 64 68 82 82
Fax : (33) 01 60 05 70 37



Member of



www.eota.eu

**European Technical
Assessment**

**ETA-16/0380
of 07/06/2016**

English translation prepared by CSTB - Original version in French language

General Part

Nom commercial
Trade name

Scell-It BZ-S

Famille de produit
Product family

Cheville métallique à expansion par vissage à couple contrôlé, de fixation dans le béton fissuré et non fissuré diamètres M8, M10, M12 et M16

Torque-controlled expansion anchor for use in cracked and uncracked concrete: sizes M8, M10, M12 and M16

Titulaire
Manufacturer

Scell-It
28, rue Paul Dubrule
59810 LESQUIN
France

Usine de fabrication e
Manufacturing plants

Plant 2 Italy

Cette évaluation contient:
This Assessment contains

18 pages incluant 15 annexes qui font partie intégrante de cette évaluation

18 pages including 15 annexes which form an integral part of this assessment

Base de l'ETE
Basis of ETA

ETAG 001, Version Avril 2013, utilisée en tant que EAD
ETAG 001, Edition April 2013 used as EAD

Cette évaluation remplace:
This Assessment replaces

Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and should be identified as such. Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may be made, with the written consent of the issuing Technical Assessment Body. Any partial reproduction has to be identified as such.

Specific Part

1 Technical description of the product

The Scell-It BZ-S wedge anchor is an anchor made of zinc electroplated steel which is placed into a drilled hole and anchored by torque-controlled expansion.

The illustration and the description of the product are given in Annexes A.

2 Specification of the intended use

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annexes B.

The provisions made in this European technical assessment are based on an assumed working life of the anchor of 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

3 Performance of the product

3.1 Mechanical resistance and stability (BWR 1)

Essential characteristic	Performance
Characteristic tension resistance acc. ETAG001, Annex C	See Annex C 1
Characteristic shear resistance acc. ETAG001, Annex C	See Annex C 2
Characteristic tension resistance acc. CEN/TS 1992-4	See Annex C 5
Characteristic shear resistance acc. CEN/TS 1992-4	See Annex C 6
Characteristic resistance under seismic action Cat 1 acc. TR045	See Annex C 9
Characteristic resistance under seismic action Cat 2 acc. TR045	See Annex C 10
Displacements	See Annex C 11

3.2 Safety in case of fire (BWR 2)

Essential characteristic	Performance
Reaction to fire	Anchorage satisfy requirements for Class A1
Characteristic tension resistance under fire acc. ETAG001, Annex C	See Annex C 3
Characteristic shear resistance under fire acc. ETAG001, Annex C	See Annex C 4
Characteristic tension resistance under fire acc. CEN/TS 1992-4	See Annex C 7
Characteristic shear resistance under fire acc. CEN/TS 1992-4	See Annex C 8

3.3 Hygiene, health and the environment (BWR 3)

Regarding dangerous substances contained in this European technical approval, there may be requirements applicable to the products falling within its scope (e.g. transposed European legislation and national laws, regulations and administrative provisions). In order to meet the provisions of the Construction Products Directive, these requirements need also to be complied with, when and where they apply.

3.4 Safety in use (BWR 4)

For Basic requirement Safety in use the same criteria are valid as for Basic Requirement Mechanical resistance and stability.

3.5 Protection against noise (BWR 5)

Not relevant.

3.6 Energy economy and heat retention (BWR 6)

Not relevant.

3.7 Sustainable use of natural resources (BWR 7)

For the sustainable use of natural resources no performance was determined for this product.

3.8 General aspects relating to fitness for use

Durability and Serviceability are only ensured if the specifications of intended use according to Annex B1 are kept.

4 Assessment and verification of constancy of performance (AVCP)

According to the Decision 96/582/EC of the European Commission¹, as amended, the system of assessment and verification of constancy of performance (see Annex V to Regulation (EU) No 305/2011) given in the following table apply.

Product	Intended use	Level or class	System
Metal anchors for use in concrete	For fixing and/or supporting to concrete, structural elements (which contributes to the stability of the works) or heavy units	—	1

5 Technical details necessary for the implementation of the AVCP system

Technical details necessary for the implementation of the Assessment and verification of constancy of performance (AVCP) system are laid down in the control plan deposited at Centre Scientifique et Technique du Bâtiment.

The manufacturer shall, on the basis of a contract, involve a notified body approved in the field of anchors for issuing the certificate of conformity CE based on the control plan.


The original French version is signed by

Charles Baloché
Technical Director

¹

Official Journal of the European Communities L 254 of 08.10.1996

Assembled anchor:

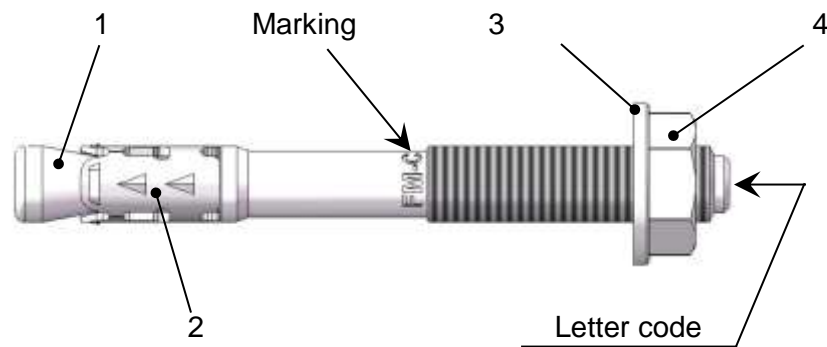

- 1. Bolt
- 2. Expansion sleeve
- 3. Washer
- 4. Hexagonal nut

Marking on the bolt:

FM-C (product name)

followed by MX/Y where

MX = thread diameter

Y = fixture thickness

Table 1: Materials

Part	Designation	Material	Protection
1	Bolt	M8 and M10: 19MnB4 DIN 1654-T4	Galvanised ¹⁾ $\geq 8\mu\text{m}$
		M12 and M16 C30BKD EU 119-74	
2	Expansion sleeve	Stainless steel X2CrNiMo 17-12-2 UNI EN 10088/2	-
3	Washer	C-steel DIN 125/1 (normal), DIN 9021 (large)	Galvanised ¹⁾ $\geq 8\mu\text{m}$
4	Hexagonal nut	C-steel DIN 934, steel grade 8	Galvanised ¹⁾ $\geq 8\mu\text{m}$

¹⁾ Special galvanised NAUTILUS Brilliant

Scell-It BZ-S anchor

Product description

Installation condition - Materials

Annex A1

Specifications of intended use

Anchorage subject to:

- Static and quasi-static loads,
- Seismic load (category C2) loads,
- Fire.

Base materials:

- Cracked concrete and non-cracked concrete
- Reinforced or unreinforced normal weight concrete of strength classes C 20/25 at least to C50/60 at most according to ENV 206: 2000-12.

Use conditions (Environmental conditions):

- Structures subject to dry internal conditions.

Design:

- The anchorages are designed in accordance with the ETAG001 Annex C "Design Method for Anchorages" or CEN/TS 1992-4-4 "Design of fastenings for use in concrete" under the responsibility of an engineer experienced in anchorages and concrete work.
- For seismic application the anchorages are designed in accordance with TR045 "Design of Metal Anchors For Use In Concrete Under Seismic Actions".
- For application with resistance under fire exposure the anchorages are designed in accordance with method given in TR020 "Evaluation of Anchorage in Concrete concerning Resistance to Fire".
- Verifiable calculation notes and drawings are prepared taking account of the loads to be anchored. The position of the anchor is indicated on the design drawings.

Installation:

- Anchor installation carried out by appropriately qualified personnel and under the supervision of the person responsible for technical matters of the site.
- Use of the anchor only as supplied by the manufacturer without exchanging the components of an anchor.
- Anchor installation in accordance with the manufacturer's specifications and drawings and using the appropriate tools.
- Effective anchorage depth, edge distances and spacing not less than the specified values without minus tolerances.
- Hole drilling by hammer drill.
- Cleaning of the hole of drilling dust.
- Application of specified torque moment using a calibrated torque wrench.
- In case of aborted hole, drilling of new hole at a minimum distance of twice the depth of the aborted hole, or smaller distance provided the aborted drill hole is filled with high strength mortar and no shear or oblique tension loads in the direction of aborted hole.



Scell-It BZ-S anchor

Intended Use
Specifications

Annex B1

Table 2: Anchor dimensions

	d x L	Marking	Letter code ID	L (mm)	d _{nom} (mm)	d _{r1} (mm)	f (mm)
M8	M8x68	FM-C 8/4	A	68	8	5,8	30
	M8x75	FM-C 8/10	B	75			30
	M8x90	FM-C 8/25	C	90			40
	M8x115	FM-C 8/50	D	115			60
	M8x135	FM-C 8/70	E	135			80
	M8x165	FM-C 8/100	G	165			80
M10	M10x90	FM-C 10/10	A	90	10	7,4	40
	M10x105	FM-C 10/25	B	105			55
	M10x115	FM-C 10/35	C	115			55
	M10x135	FM-C 10/55	D	135			85
	M10x155	FM-C 10/75	E	155			85
	M10x185	FM-C 10/105	F	185			85
M12	M12x110	FM-C 12/10	A	110	12	8,8	65
	M12x120	FM-C 12/20	B	120			65
	M12x145	FM-C 12/45	C	145			85
	M12x170	FM-C 12/70	D	170			85
	M12x200	FM-C 12/100	E	200			85
M16	M16x130	FM-C 16/10	A	130	16	11,8	65
	M16x150	FM-C 16/30	B	150			85
	M16x185	FM-C 16/60	C	185			85
	M16x220	FM-C 16/100	D	220			85

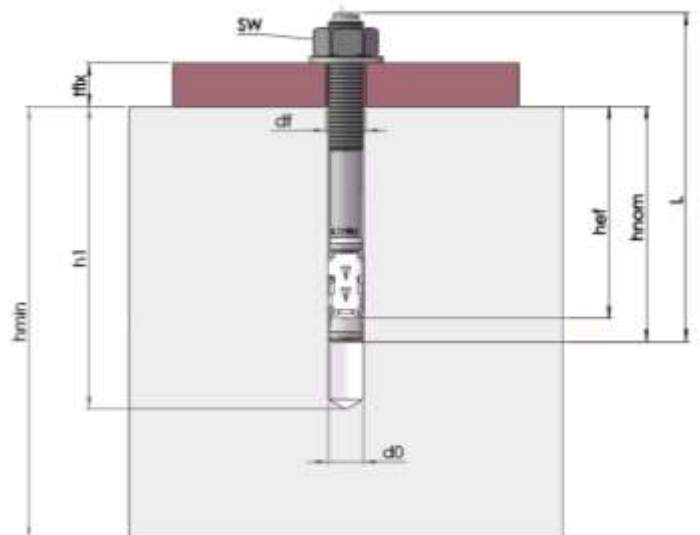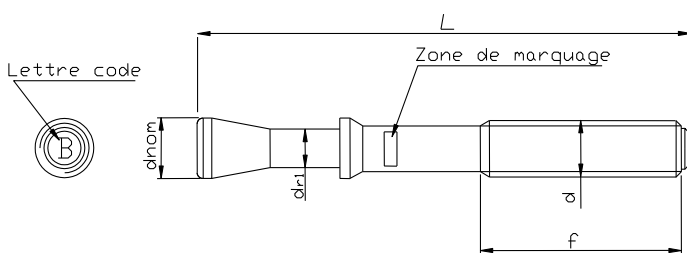

Scell-It BZ-S anchor

Intended Use

Installation parameters

Annex B2

Table 3: Installation data

	dxL	ID	t _{fix} (mm)	d ₀ (mm)	h ₁ (mm)	h _{nom} (mm)	h _{ef} (mm)	d _f (mm)	h _{min} (mm)	T _{inst} (Nm)	sw (mm)	Marking
M8	M8x68	A	4	8	70	54	48	9	100	20	13	FM-C 8/4
	M8x75	B	10									FM-C 8/10
	M8x90	C	25									FM-C 8/25
	M8x115	D	50									FM-C 8/50
	M8x135	E	70									FM-C 8/70
	M8x165	G	100									FM-C 8/100
M10	M10x90	A	10	10	80	67	60	12	120	40	17	FM-C 10/10
	M10x105	B	25									FM-C 10/25
	M10x115	C	35									FM-C 10/35
	M10x135	D	55									FM-C 10/55
	M10x155	E	75									FM-C 10/75
	M10x185	F	105									FM-C 10/105
M12	M12x110	A	10	12	100	81	72	14	150	60	19	FM-C 12/10
	M12x120	B	20									FM-C 12/20
	M12x145	C	45									FM-C 12/45
	M12x170	D	70									FM-C 12/70
	M12x200	E	100									FM-C 12/100
M16	M16x130	A	10	16	115	97	86	18	170	120	24	FM-C 16/10
	M16x150	B	30									FM-C 16/30
	M16x185	C	60									FM-C 16/60
	M16x220	D	100									FM-C 16/100

				M8	M10	M12	M16
Min. member thickness	h _{min}	[mm]		100	120	150	170
Minimum edge distance	c _{min}	[mm]		50	60	70	85
Corresponding spacing	s ≥	[mm]		75	120	150	170
Minimum spacing	s _{min}	[mm]		50	60	70	80
Corresponding edge distance	c ≥	[mm]		65	80	90	120

Scell-It BZ-S anchor

Intended Use

Installation parameters

Annex B3

Table 4: Characteristic values for tension loads in case of static and quasi static loading for design method A acc. ETAG001, Annex C

			M8	M10	M12	M16
Steel failure						
Char. resistance	$N_{Rk,s}$	[kN]	23,8	38,7	54,7	98,4
Partial safety factor	$\gamma_{Ms}^{1)}$	[-]	1,5			

Pullout failure $N_{Rk,p} = \Psi_c \times N^0_{Rk,p}$							
Char. resistance in concrete C20/25	non-cracked	$N^0_{Rk,p}$	[kN]	9	16	20	35
	cracked	$N^0_{Rk,p}$	[kN]	6	12	16	20
Partial safety factor for cracked or non-cracked concrete		$\gamma_{Mp}^{1)}$	[-]	1,5 ²⁾			
Increasing factor for N_{RK}	concrete C30/37	Ψ_c	[-]	1,22			
	concrete C40/50		[-]	1,41			
	concrete C50/60		[-]	1,55			

Concrete cone failure and splitting failure							
Effective embedment depth		h_{ef}	[mm]	48	60	72	86
Partial safety factor for cracked or non-cracked concrete		$\gamma_{Mc} = \gamma_{Msp}^{1)}$		1,5 ²⁾			
Increasing factor for N_{RK}	concrete C30/37	Ψ_c	[-]	1,22			
	concrete C40/50		[-]	1,41			
	concrete C50/60		[-]	1,55			
Char. spacing	concrete cone failure	$s_{cr,N}$	[mm]	140	180	220	260
	splitting failure	$s_{cr,sp}$	[mm]	290	360	430	520
Char. edge distance	concrete cone failure	$c_{cr,N}$	[mm]	70	90	110	130
	splitting failure	$c_{cr,sp}$	[mm]	145	180	215	260

¹⁾ In absence of other national regulations

²⁾ The value contains an installation safety factor $\gamma_2 = 1.0$

Scell-It BZ-S anchor

Design according to ETAG001, Annex C
Characteristic resistance under tension loads

Annex C1

Table 5: Characteristic values for shear loads in case of static and quasi static loading for design design method A acc. ETAG001, Annex C

			M8	M10	M12	M16
Steel failure without lever arm						
Char. resistance	$V_{Rk,s}$	[kN]	12,9	24,2	33,8	66,4
Partial safety factor	$\gamma_{Ms}^{1)}$	[-]	1,5			
Steel failure with lever arm						
Char. bending resistance	$M^0_{Rk,s}$	[Nm]	34	67	118	300
Partial safety factor	$\gamma_{Ms}^{1)}$	[-]	1,5			
Concrete pry-out failure						
Factor in equation (5.6) of ETAG Annex C, § 5.2.3.3	k	[-]	1,0	2,0	2,0	2,0
Partial safety factor	$\gamma_{Mc}^{1)}$	[-]	1,5 ¹⁾			
Concrete edge failure						
Effective length of anchor under shear loading	l_f	[mm]	48	60	72	86
Outside diameter of anchor	d_{nom}	[mm]	8	10	12	16
Partial safety factor	$\gamma_{Mc}^{1)}$	[-]	1,5 ¹⁾			

¹⁾ The installation safety factor $\gamma_2 = 1.0$ is included

Scell-It BZ-S anchor

Design according to ETAG001, Annex C
Characteristic resistance under shear loads

Annex C2

Table 6: Characteristic tension resistance in cracked and non-cracked concrete under fire exposure for design method A acc. ETAG001, Annex C

			M8	M10	M12	M16
Steel failure						
Characteristic resistance	R30 $N_{Rk,s,fi}$	[kN]	0,4	0,9	1,7	3,1
	R60 $N_{Rk,s,fi}$	[kN]	0,3	0,8	1,3	2,4
	R90 $N_{Rk,s,fi}$	[kN]	0,3	0,6	1,1	2,0
	R120 $N_{Rk,s,fi}$	[kN]	0,2	0,5	0,8	1,6
Pullout failure (cracked and non-cracked concrete)						
Char. resistance in concrete $\geq C20/25$	R30 $N_{Rk,p,fi}$	[kN]	1,5	3,0	4,0	5,0
	R60 $N_{Rk,p,fi}$	[kN]	1,5	3,0	4,0	5,0
	R90 $N_{Rk,p,fi}$	[kN]	1,5	3,0	4,0	5,0
	R120 $N_{Rk,p,fi}$	[kN]	1,2	2,4	3,2	4,0
Concrete cone and splitting failure²⁾ (cracked and non-cracked concrete)						
Char. resistance in concrete $\geq C20/25$	R30 $N^0_{Rk,c,fi}$	[kN]	2,9	5,0	7,9	12,3
	R60 $N^0_{Rk,c,fi}$	[kN]	2,9	5,0	7,9	12,3
	R90 $N^0_{Rk,c,fi}$	[kN]	2,9	5,0	7,9	12,3
	R120 $N^0_{Rk,c,fi}$	[kN]	2,3	4,0	6,3	9,9
Characteristic spacing	$s_{cr,N,fi}$	[mm]	4 x h_{ef}			
Characteristic edge distance	$c_{cr,N,fi}$	[mm]	2 x h_{ef}			

¹⁾ Design under fire exposure is performed according to the design method given in TR 020. Under fire exposure usually cracked concrete is assumed. The design equations are given in TR 020, Section 2.2.1.

²⁾ As a rule, splitting failure can be neglected when cracked concrete and reinforcement is assumed.

TR 020 covers design for fire exposure from one side. For fire attack from more than one side the edge distance must be increased to $c_{min} \geq 300$ mm and $\geq 2 \cdot h_{ef}$.

Scell-It BZ-S anchor

Design according to ETAG001, Annex C

Characteristic tension resistance under fire exposure

Annex C3

Table 7: Characteristic shear resistance in cracked and non-cracked concrete under fire exposure for design method A acc. ETAG001, Annex C

			M8	M10	M12	M16
Steel failure without lever arm						
Characteristic resistance	R30 $V_{Rk,s,fi}$	[kN]	0,4	0,9	1,7	3,1
	R60 $V_{Rk,s,fi}$	[kN]	0,3	0,8	1,3	2,4
	R90 $V_{Rk,s,fi}$	[kN]	0,3	0,6	1,1	2,0
	R120 $V_{Rk,s,fi}$	[kN]	0,2	0,5	0,8	1,6
Steel failure with lever arm						
Characteristic bending moment	R30 $M^0_{Rk,s,fi}$	[Nm]	0,4	1,1	2,6	6,7
	R60 $M^0_{Rk,s,fi}$	[Nm]	0,3	1,0	2,0	5,0
	R90 $M^0_{Rk,s,fi}$	[Nm]	0,3	0,7	1,7	4,3
	R120 $M^0_{Rk,s,fi}$	[Nm]	0,2	0,6	1,3	3,3
Concrete pry-out failure						
Factor in equation (5.6) of ETAG Annex C, § 5.2.3.3	k	[-]	1,0	2,0	2,0	2,0
Characteristic resistance	R30 $V_{Rk,cp,fi}$	[kN]	2,9	10,0	15,8	24,7
	R60 $V_{Rk,cp,fi}$	[kN]	2,9	10,0	15,8	24,7
	R90 $V_{Rk,cp,fi}$	[kN]	2,9	10,0	15,8	24,7
	R120 $V_{Rk,cp,fi}$	[kN]	2,3	8,0	12,7	19,8
Concrete edge failure						
Eff. length of anchor under shear loading	l_f	[mm]	48	60	72	86
Outside diameter of anchor	d_{nom}	[mm]	8	10	12	16

¹⁾ Design under fire exposure is performed according to the design method given in TR 020. Under fire exposure usually cracked concrete is assumed. The design equations are given in TR 020, Section 2.2.2.

TR 020 covers design for fire exposure from one side. For fire attack from more than one side the edge distance must be increased to $c_{min} \geq 300$ mm and $\geq 2 \cdot h_{ef}$.

Scell-It BZ-S anchor

Design according to ETAG001, Annex C

Characteristic shear resistance under fire exposure

Annex C4

Table 8: Characteristic values for tension loads in case of static and quasi static loading for design method A acc. CEN/TS 1992-4

			M8	M10	M12	M16	
Steel failure							
Char. resistance	N _{Rk,s}	[kN]	23,8	38,7	54,7	98,4	
Partial safety factor	γ _{Ms} ¹⁾	[-]	1,5				
Pullout failure N _{Rk,p} = Ψ _c x N ⁰ _{Rk,p}							
Char. resistance in concrete C20/25	non-cracked	N ⁰ _{Rk,p}	[kN]	9	16	20	35
	cracked	N ⁰ _{Rk,p}	[kN]	6	12	16	20
Partial safety factor for cracked or non-cracked concrete		γ _{Mp} ¹⁾	[-]	1,5 ²⁾			
Increasing factor for N _{Rk,p}	concrete C30/37	Ψ _c	[-]	1,22			
	concrete C40/50		[-]	1,41			
	concrete C50/60		[-]	1,55			
Concrete cone failure and splitting failure							
Effective embedment depth		h _{ef}	[mm]	48	60	72	86
Factor for cracked concrete		k _{cr}		7,2			
Factor for non cracked concrete		k _{ucr}		10,1			
Partial safety factor		γ _{Mc} =γ _{Msp} ¹⁾		1,5 ²⁾			
Char. spacing	concrete cone failure	s _{cr,N}	[mm]	140	180	220	260
	splitting failure	s _{cr,sp}	[mm]	290	360	430	520
Char. edge distance	concrete cone failure	c _{cr,N}	[mm]	70	90	110	130
	splitting failure	c _{cr,sp}	[mm]	145	180	215	260

¹⁾ In absence of other national regulations

²⁾ The value contains an installation safety factor $\gamma_2 = 1.0$

Scell-It BZ-S anchor

Design according to CEN/TS 1992-4

Characteristic resistance under tension loads

Annex C5

Table 9: Characteristic values for shear loads in case of static and quasi static loading for design design method A acc. CEN/TS 1992-4

			M8	M10	M12	M16
Steel failure without lever arm						
Char. resistance	$V_{Rk,s}$	[kN]	12,9	24,2	33,8	66,4
Factor considering ductility	k_2	[-]	0,8			
Partial safety factor	$\gamma_{Ms}^{1)}$	[-]	1,5			

Steel failure with lever arm						
Char. bending moment	$M^0_{Rk,s}$	[Nm]	34	67	118	300
Partial safety factor	$\gamma_{Ms}^{1)}$	[-]	1,5			

Concrete pry-out failure						
Factor in equation (16) of CEN TS 1992-4-4, § 6.2.2.3	k_3	[-]	1,0	2,0	2,0	2,0
Partial safety factor	$\gamma_{Mc}^{1)}$	[-]	1,5 ¹⁾			

Concrete edge failure						
Effective length of anchor under shear loading	l_f	[mm]	48	60	72	86
Outside diameter of anchor	d_{nom}	[mm]	8	10	12	16
Partial safety factor	$\gamma_{Mc}^{1)}$	[-]	1,5 ¹⁾			

¹⁾ The installation safety factor $\gamma_2 = 1.0$ is included

Scell-It BZ-S anchor

Design according to **CEN/TS 1992-4**
Characteristic resistance under shear loads

Annex C6

Table 10: Characteristic tension resistance in cracked and non-cracked concrete under fire exposure for design method A acc. CEN/TS 1992-4

			M8	M10	M12	M16
Steel failure						
Characteristic resistance	R30 $N_{Rk,s,fi}$	[kN]	0,4	0,9	1,7	3,1
	R60 $N_{Rk,s,fi}$	[kN]	0,3	0,8	1,3	2,4
	R90 $N_{Rk,s,fi}$	[kN]	0,3	0,6	1,1	2,0
	R120 $N_{Rk,s,fi}$	[kN]	0,2	0,5	0,8	1,6
Pullout failure (cracked and non-cracked concrete)						
Char. resistance in concrete $\geq C20/25$	R30 $N_{Rk,p,fi}$	[kN]	1,5	3,0	4,0	5,0
	R60 $N_{Rk,p,fi}$	[kN]	1,5	3,0	4,0	5,0
	R90 $N_{Rk,p,fi}$	[kN]	1,5	3,0	4,0	5,0
	R120 $N_{Rk,p,fi}$	[kN]	1,2	2,4	3,2	4,0
Concrete cone and splitting failure²⁾ (cracked and non-cracked concrete)						
Char. resistance in concrete $\geq C20/25$	R30 $N^0_{Rk,c,fi}$	[kN]	2,9	5,0	7,9	12,3
	R60 $N^0_{Rk,c,fi}$	[kN]	2,9	5,0	7,9	12,3
	R90 $N^0_{Rk,c,fi}$	[kN]	2,9	5,0	7,9	12,3
	R120 $N^0_{Rk,c,fi}$	[kN]	2,3	4,0	6,3	9,9
Characteristic spacing	$s_{cr,N,fi}$	[mm]	4 x h_{ef}			
Characteristic edge distance	$c_{cr,N,fi}$	[mm]	2 x h_{ef}			

¹⁾ Design under fire exposure is performed according to the design method given in TR 020. Under fire exposure usually cracked concrete is assumed. The design equations are given in TR 020, Section 2.2.1.

²⁾ As a rule, splitting failure can be neglected when cracked concrete and reinforcement is assumed.

TR 020 covers design for fire exposure from one side. For fire attack from more than one side the edge distance must be increased to $c_{min} \geq 300$ mm and $\geq 2 \cdot h_{ef}$.

Scell-It BZ-S anchor

Design according to **CEN/TS 1992-4**
Characteristic tension resistance under fire exposure

Annex C7

Table 11: Characteristic shear resistance in cracked and non-cracked concrete under fire exposure for design method A acc. CEN/TS 1992-4

			M8	M10	M12	M16
Steel failure without lever arm						
Characteristic resistance	R30 $V_{Rk,s,fi}$	[kN]	0,4	0,9	1,7	3,1
	R60 $V_{Rk,s,fi}$	[kN]	0,3	0,8	1,3	2,4
	R90 $V_{Rk,s,fi}$	[kN]	0,3	0,6	1,1	2,0
	R120 $V_{Rk,s,fi}$	[kN]	0,2	0,5	0,8	1,6
Steel failure with lever arm						
Characteristic bending moment	R30 $M^0_{Rk,s,fi}$	[Nm]	0,4	1,1	2,6	6,7
	R60 $M^0_{Rk,s,fi}$	[Nm]	0,3	1,0	2,0	5,0
	R90 $M^0_{Rk,s,fi}$	[Nm]	0,3	0,7	1,7	4,3
	R120 $M^0_{Rk,s,fi}$	[Nm]	0,2	0,6	1,3	3,3
Concrete pry-out failure						
Factor in equation (16) of CEN TS 1992-4-4, § 6.2.2.3	k_3	[-]	1,0	2,0	2,0	2,0
Characteristic resistance	R30 $V_{Rk,cp,fi}$	[kN]	2,9	10,0	15,8	24,7
	R60 $V_{Rk,cp,fi}$	[kN]	2,9	10,0	15,8	24,7
	R90 $V_{Rk,cp,fi}$	[kN]	2,9	10,0	15,8	24,7
	R120 $V_{Rk,cp,fi}$	[kN]	2,3	8,0	12,7	19,8
Concrete edge failure						
Eff. length of anchor under shear loading	l_f	[mm]	48	60	72	86
Outside diameter of anchor	d_{nom}	[mm]	8	10	12	16

¹⁾ Design under fire exposure is performed according to the design method given in TR 020. Under fire exposure usually cracked concrete is assumed. The design equations are given in TR 020, Section 2.2.2.

TR 020 covers design for fire exposure from one side. For fire attack from more than one side the edge distance must be increased to $c_{min} \geq 300$ mm and $\geq 2 \cdot h_{ef}$.

Scell-It BZ-S anchor

Design according to **CEN/TS 1992-4**
Characteristic shear resistance under fire exposure

Annex C8

Table 12: Characteristic values for resistance in case of seismic performance category C1 acc. TR045 "Design of Metal anchor under Seismic Actions"

Anchor sizes			M8	M10	M12	M16
Tension load						
Steel failure						
Characteristic resistance		$N_{Rk,s,seis}$ [kN]	23,8	38,7	54,7	98,4
Partial safety factor ¹⁾		$\gamma_{Ms,seis}$ [-]	1,5			
Pull-out failure $N_{Rk,p,seis} = \Psi_c \times N_{Rk,p,seis}^0$						
Characteristic resistance		$N_{Rk,p,seis}^0$ [kN]	6	12	16	20
Partial safety factor ¹⁾		$\gamma_{Mp, seis}$ [-]	1,5			
Shear loads						
Steel failure without lever arm						
Characteristic resistance		$V_{Rk,s,seis}$ [kN]	7,7	17,0	30,4	57,6
Partial safety factor ¹⁾		$\gamma_{Ms, seis}$ [-]	1,5			

¹⁾ The recommended partial safety factors under seismic action ($\gamma_{M,seis}$) are the same as for static loading

Scell-It BZ-S anchor

Design according to TR045
Characteristic resistance under seismic actions

Annex C9

Table 13: Characteristic values for resistance in case of seismic performance category C2 acc. TR045 “Design of Metal anchor under Seismic Actions”

Anchor sizes			M8	M10	M12	M16
Tension load						
Steel failure						
Characteristic resistance ²⁾	N _{Rk,s,seis}	[kN]	-	38,7	54,7	98,4
Partial safety factor ³⁾	γ _{Ms,seis}	[-]	1,5			
Pull-out failure N _{Rk,p,seis} = Ψ _c x N ⁰ _{Rk,p,seis}						
Characteristic resistance ²⁾	N ⁰ _{Rk,p,seis}	[kN]	-	3,3	11,8	20,0
Partial safety factor ³⁾	γ _{Mp, seis}	[-]	1,5			
Displacement at DLS ^{1) 2)}	δ _{N,sei} (DSL)	[mm]	-	2,5	5,0	4,4
Displacement at DLS ^{1) 2)}	δ _{N,sei} (ULS)	[mm]	-	10,7	20,4	17,8
Shear loads						
Steel failure without lever arm						
Characteristic resistance ²⁾	V _{Rk,s,seis}	[kN]	-	11,9	19,3	31,2
Partial safety factor ³⁾	γ _{Ms, seis}	[-]	1,5			
Displacement at DLS ^{1) 2)}	δ _{V,sei} (DSL)	[mm]	-	5,0	7,0	7,0
Displacement at DLS ^{1) 2)}	δ _{V,sei} (ULS)	[mm]	-	7,1	9,1	6,6

1) The listed displacements represent mean values.

2) A smaller displacement may be required in the design provisions stated in section “Design of Anchorage”, e.g. in the case of displacement sensitive fastenings or “rigid” supports. The characteristic resistance associated with such smaller displacement may be determined by linear interpolation or proportional reduction.

3) The recommended partial safety factors under seismic action ($\gamma_{M,seis}$) are the same as for static loading.

Scell-It BZ-S anchor

Design according to TR045

Characteristic resistance under seismic actions

Annex C10

Table 14: Displacements under tension loading

		M8	M10	M12	M16
Tension load in non-cracked concrete C20/25 [kN]		4,29	7,62	9,52	16,67
Displacement	δ_{N0} [mm]	0,1	0,1	0,1	0,1
	$\delta_{N\infty}$ [mm]	0,5	0,5	0,5	0,5
Tension load in non-cracked concrete C50/60 [kN]		6,64	11,91	14,76	25,83
Displacement	δ_{N0} [mm]	0,1	0,2	0,2	0,3
	$\delta_{N\infty}$ [mm]	0,5	0,5	0,5	0,5
Tension load in cracked concrete C20/25 [kN]		2,86	5,71	7,62	9,52
Displacement	δ_{N0} [mm]	1,4	1,2	0,9	0,6
	$\delta_{N\infty}$ [mm]	1,4	1,2	1,3	0,6
Tension load in cracked concrete C50/60 [kN]		4,43	8,86	11,81	14,76
Displacement	δ_{N0} [mm]	1,8	1,8	1,8	1,8
	$\delta_{N\infty}$ [mm]	1,8	1,8	1,8	1,8

Table 15: Displacements under shear loads

		M8	M10	M12	M16
Shear load in cracked and non-cracked concrete C20/25 to C50/60 [kN]		6,19	11,43	16,19	31,43
Displacement	δ_{V0} [mm]	2,3	2,6	2,9	3,3
	$\delta_{V\infty}$ [mm]	3,4	3,9	4,3	4,9

Additional displacement due to anular gap between anchor and fixture is to be taken into account.

Scell-It BZ-S anchor

Design
Displacements

Annex C11