# HVE









Approval body for construction products and types of construction

#### **Bautechnisches Prüfamt**

An institution established by the Federal and Laender Governments



### European Technical Assessment

### ETA-10/0060 of 11 June 2015

English translation prepared by DIBt - Original version in German language

### **General Part**

Technical Assessment Body issuing the Deutsches Institut für Bautechnik **European Technical Assessment:** Tecfi HVE Rock Trade name of the construction product Product family Torque controlled expansion anchor for use in concrete to which the construction product belongs Manufacturer Tecfi S.p.A Strada Statale Appia, Km. 193 81050 PASTORANO (CE) ITALIEN Manufacturing plant Tecfi S.p.A. Italy This European Technical Assessment 15 pages including 3 annexes contains This European Technical Assessment is Guideline for European technical approval of "Metal issued in accordance with Regulation (EU) anchors for use in concrete", ETAG 001 Part 2: "Torque controlled expansion anchors", April 2013, No 305/2011, on the basis of used as European Assessment Document (EAD) according to Article 66 Paragraph 3 of Regulation (EU) No 305/2011.

Deutsches Institut für Bautechnik Kolonnenstraße 30 B | 10829 Berlin | GERMANY | Phone: +49 30 78730-0 | Fax: +49 30 78730-320 | Email: dibt@dibt.de | www.dibt.de



### **European Technical Assessment** ETA-10/0060

Page 2 of 15 | 11 June 2015

English translation prepared by DIBt

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction has to be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission according to Article 25 Paragraph 3 of Regulation (EU) No 305/2011.



Page 3 of 15 | 11 June 2015

### European Technical Assessment ETA-10/0060 English translation prepared by DIBt

### Specific Part

### 1 Technical description of the product

The Tecfi HVE Rock is an anchor made of galvanised steel of sizes M6, M8, M10, M12 and M16 which is placed into a drilled hole and anchored by torque-controlled expansion. The product description is given in Annex A.

# 2 Specification of the intended use in accordance with the applicable European Assessment Document

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

### 3 Performance of the product and references to the methods used for its assessment

### 3.1 Mechanical resistance and stability (BWR 1)

| Essential characteristic   | Performance   |
|--|---------------|
| Characteristic resistance for static and quasi static action and seismic performance category C1 | See Annex C 1 |
| Displacements  | See Annex C 4 |

### 3.2 Safety in case of fire (BWR 2)

| Essential characteristic | Performance                                     |
|--------------------------|---|
| Reaction to fire         | Anchorages satisfy requirements for<br>Class A1 |
| Resistance to fire       | See Annex C 2 / C 3                             |

### **3.3 Hygiene, health and the environment (BWR 3)** Not applicable.

### 3.4 Safety in use (BWR 4)

The essential characteristics regarding Safety in use are included under the Basic Works Requirement Mechanical resistance and stability.

3.5 Protection against noise (BWR 5)

Not applicable.

3.6 Energy economy and heat retention (BWR 6)

Not applicable.

### 3.7 Sustainable use of natural resources (BWR 7)

The sustainable use of natural resources was not investigated.



### European Technical Assessment ETA-10/0060

### Page 4 of 15 | 11 June 2015

English translation prepared by DIBt

### 3.8 General aspects

The verification of durability is part of testing the essential characteristics. Durability is only ensured if the specifications of intended use according to Annex B are taken into account.

# 4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

According to Decision of the Commission of 24 June 1996 (96/582/EC) (OJ L 254 of 08.10.96 p. 62-65), the system of assessment and verification of constancy of performance (see Annex V and Article 65 Paragraph 2 to Regulation (EU) No 305/2011) given in the following table applies.

| Product   | Intended use  | Level or class | System |
|---|---|----------------|--------|
| Metal anchors for use in concrete (heavy-duty type) | For fixing and/or supporting<br>concrete structural elements or<br>heavy units such as cladding and<br>suspended ceilings | _              | 1      |


### 5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited at Deutsches Institut für Bautechnik.


Issued in Berlin on 11 June 2015 by Deutsches Institut für Bautechnik

Andreas Kummerow p.p. Head of Department *beglaubigt:* Lange



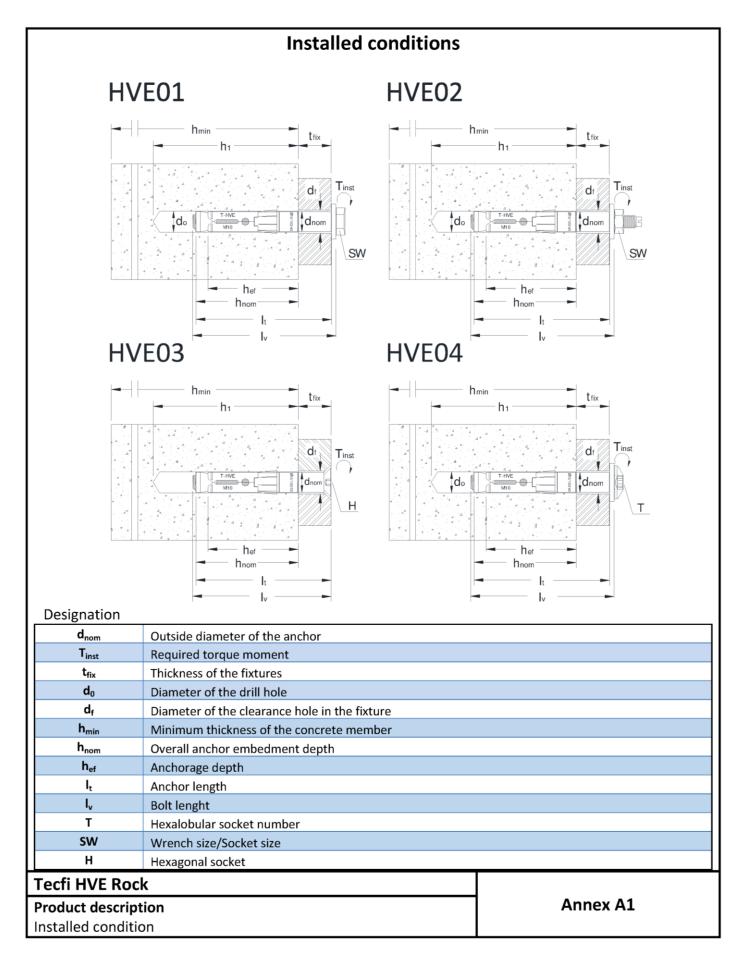



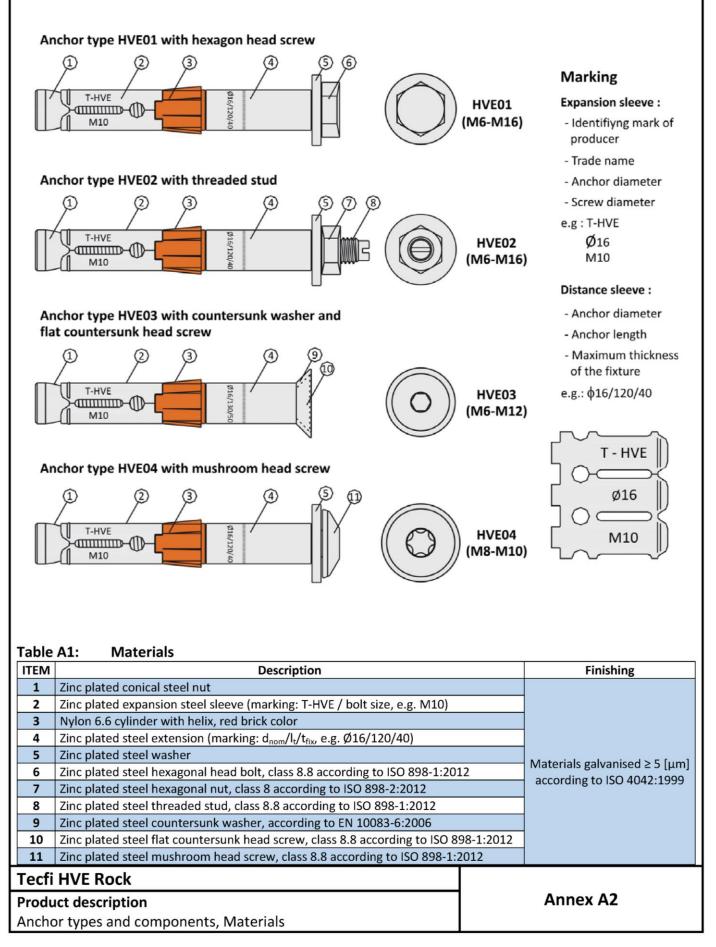

# Page 7 of European Technical Assessment ETA-10/0060 of 11 June 2015

English translation prepared by DIBt



| HVE0<br>(M6-M: |    | HVE03<br>(M6-M12) | HVE04<br>(M8-M10) |
|----------------|----|-------------------|-------------------|
|                |    |                   | $\bigcirc$        |
| - SW           | SW | - <b></b> H       | т                 |

### Table A2: HVE01 dimensions

| Item      | Outside diameter of<br>anchor<br>[mm] | Outside diameter of<br>metric thread<br>[mm] | Length range<br>[mm] | Maximum thickness<br>of fixture range<br>[mm] |
|-----------|---------------------------------------|--|----------------------|---|
| HVE01-M6  | 10                                    | 6  | 70 - 120             | 5 - 15  |
| HVE01-M8  | 12                                    | 8  | 80 - 140             | 10 - 70                                       |
| HVE01-M10 | 16                                    | 10   | 100 - 160            | 20 - 80                                       |
| HVE01-M12 | 18                                    | 12   | 120 - 200            | 20 - 100                                      |
| HVE01-M16 | 24                                    | 16   | 140 – 220            | 20 - 100                                      |

### Table A3: HVE02 dimensions

| Item      | Outside diameter of<br>anchor<br>[mm] | Outside diameter of<br>metric thread<br>[mm] | Length range<br>[mm] | Maximum thickness<br>of fixture range<br>[mm] |
|-----------|---------------------------------------|--|----------------------|---|
| HVE02-M6  | 10                                    | 6  | 70 - 120             | 5 - 15  |
| HVE02-M8  | 12                                    | 8  | 80 - 140             | 10 - 70                                       |
| HVE02-M10 | 16                                    | 10   | 100 - 160            | 20 - 80                                       |
| HVE02-M12 | 18                                    | 12 120 - 200                                 |                      | 20 - 100                                      |
| HVE02-M16 | 24                                    | 16   | 140 – 220            | 20 - 100                                      |

### Table A4: HVE03 dimensions

| ltem      | Outside diameter of<br>anchor<br>[mm] | Outside diameter of<br>metric thread<br>[mm] | Length range<br>[mm] | Maximum thickness<br>of fixture range<br>[mm] |
|-----------|---------------------------------------|--|----------------------|---|
| HVE03-M6  | 10                                    | 6  | 85 - 125             | 20 - 60                                       |
| HVE03-M8  | 12                                    | 8  | 85 - 125             | 15 - 55                                       |
| HVE03-M10 | 16                                    | 10   | 110 - 130            | 30 - 50                                       |
| HVE03-M12 | 18                                    | 12   | 120 - 140            | 20 - 40                                       |

### Table A5: HVE04 dimensions

| ltem      | Outside diameter of<br>anchor<br>[mm] | Outside diameter of<br>metric thread<br>[mm] | Length range<br>[mm] | Maximum thickness<br>of fixture range<br>[mm] |
|-----------|---------------------------------------|--|----------------------|---|
| HVE04-M8  | 12                                    | 8  | 80 - 120             | 10 - 50                                       |
| HVE04-M10 | 16                                    | 10   | 100 - 120            | 20 - 40                                       |

| Tecfi HVE Rock      |          |
|---------------------|----------|
| Product description | Annex A3 |
| Anchor's dimensions |          |

### Page 8 of European Technical Assessment ETA-10/0060 of 11 June 2015

English translation prepared by DIBt



### Specifications of intended use

### Anchorages subject to:

- Static and quasi-static loads: all sizes
- Seismic action for Performance Category C1: all sizes
- Fire exposure: all sizes

#### **Base materials:**

- Reinforced or unreinforced normal weight concrete according to EN 206:2013.
- Strength classes C20/25 to C50/60 according to EN 206:2013.
- Non-cracked or cracked concrete

#### Use conditions (Environmental conditions):

Anchorages subject to dry internal conditions

#### Design:

- Anchorages are designed under the responsibility of an engineer experienced in anchorages and concrete work.
- Verifiable calculation notes and drawings are prepared taking account of the loads to be anchored. The position of the
  anchor is indicated on the design drawings (e.g. position of the anchor relative to reinforcement or to supports, etc.).
- Anchorages under static or quasi-static actions and under fire exposure are designed in accordance with:
- ETAG 001, Annex C, design method A, Edition August 2010;
- CEN TS CEN/TS 1992-4-1:2009;
- Anchorages under seismic actions (cracked concrete) are designed in accordance with:
  - EOTA Technical Report TR 045, Edition February 2013
  - Anchorages shall be positioned outside of critical regions (e.g. plastic hinges) of the concrete structure
  - Fastening in stand-off installation or with a grout layer are not allowed
- Anchorages under fire exposure are designed in accordance with:
  - ETAG 001, Annex C, design method A, Edition August 2010 and EOTA Technical Report TR 020, Edition May 2004
  - CEN/TS 1992-4: 2009, Annex D
  - It must be ensured that local spalling of the concrete cover does not occur

#### Installation:

- Hole drilling by rotary plus hammer mode
- Anchor installation carried out by appropriately qualified personnel and under the supervision of the person responsible for technical matters of the site.
- In case of aborted hole: new drilling at a minimum distance away of twice the depth of the aborted hole or smaller distance if the aborted hole is filled with high strength mortar and if under shear or oblique tension load it is not the direction of the load application.

### Tecfi HVE Rock

Intended use Specifications Annex B1

### Deutsches Institut für Bautechnik

| Sizes                                 |                          | HVE<br>M6 | HVE<br>M8 | HVE<br>M10 | HVE<br>M12 | HVE<br>M16 |
|---------------------------------------|--------------------------|-----------|-----------|------------|------------|------------|
| Nominal drill hole diameter           | d <sub>o</sub> =[mm]     | 10        | 12        | 16         | 18         | 24         |
| Cutting diameter of drill bit         | d <sub>cut</sub> ≤ [mm]  | 10,45     | 12,50     | 16,50      | 18,50      | 24,55      |
| Effective anchorage depth             | h <sub>ef</sub> =[mm]    | 55        | 60        | 70         | 90         | 105        |
| Depth of drill hole                   | h <sub>1</sub> = [mm]    | 80        | 90        | 100        | 120        | 140        |
| Diameter of clearance in the fixture  | d <sub>f</sub> =[mm]     | 12        | 14        | 18         | 20         | 26         |
| Overall anchor embedment depth in the | h <sub>nom</sub> = [mm]  | 65        | 70        | 80         | 100        | 120        |
| Required torque moment                | T <sub>inst</sub> = [Nm] | 15        | 30        | 50         | 100        | 160        |
| Outside diameter of anchor            | d <sub>nom</sub> = [mm]  | 10        | 12        | 16         | 18         | 24         |
| Minimum thickness of concrete member  | h <sub>min</sub> = [mm]  | 110       | 120       | 140        | 180        | 210        |
| Minimum edge distance                 | c <sub>min</sub> = [mm]  | 70        | 100       | 90         | 175        | 180        |
| Corresponding spacing                 | s≥ [mm]                  | 110       | 160       | 175        | 255        | 290        |
| Minimum spacing                       | s <sub>min</sub> = [mm]  | 55        | 110       | 80         | 135        | 130        |
| Corresponding edge distance           | c≥ [mm]                  | 110       | 145       | 120        | 220        | 240        |

| HVE01    | HVE02    | HVE03    | HVE04    |
|----------|----------|----------|----------|
| (M6-M16) | (M6-M16) | (M6-M12) | (M8-M10) |
|          |          |          |          |



### Table B2: Wrenches, sockets and maximum thickness of fixture

| Sizes                              |                             | M6 | M8 | M10 | M12 | M16 |
|------------------------------------|-----------------------------|----|----|-----|-----|-----|
| HVE 01 – Wrench size               | SW = [mm]                   | 10 | 13 | 17  | 19  | 24  |
|                                    | t <sub>fix,max</sub> = [mm] | 55 | 70 | 80  | 100 | 100 |
| HVE 01 – Thickness of fixture      | t <sub>fix,min</sub> = [mm] | 5  | 10 | 20  | 20  | 20  |
| HVE 02 – Wrench size               | SW = [mm]                   | 10 | 13 | 17  | 19  | 24  |
| HVE 02 – Thickness of fixture      | t <sub>fix,max</sub> = [mm] | 55 | 70 | 80  | 100 | 100 |
|                                    | t <sub>fix,min</sub> = [mm] | 5  | 10 | 20  | 20  | 20  |
| HVE 03 – Hexagonal socket size     | H = [mm]                    | 4  | 5  | 6   | 8   | -   |
| HVE 03 – Thickness of fixture      | t <sub>fix,max</sub> = [mm] | 60 | 55 | 50  | 100 | -   |
| HVE 05 – Thickness of fixture      | t <sub>fix,min</sub> = [mm] | 20 | 15 | 30  | 20  | -   |
| HVE 04 – Hexalobular socket number | T = [-]                     | -  | 40 | 40  | -   | -   |
| HVE 04 – Thickness of fixture      | t <sub>fix,max</sub> = [mm] | -  | 50 | 40  | -   | -   |
|                                    | t <sub>fix,min</sub> = [mm] | -  | 10 | 20  | -   | -   |

| Tecfi HVE Rock                                     |            |
|--|------------|
| Intended use                                       | Annex B2   |
| Installation parameters                            | Allitex D2 |
| Wrenches, sockets and maximum thickness of fixture |            |



| Drill bit                   |             |  |                     |  |  |  |  |
|-----------------------------|-------------|--|---------------------|--|--|--|--|
|                             | Anchor size |  | Drill bit item code |  |  |  |  |
| 111                         | M6 / Ø10    |  | EO 01 08 210        |  |  |  |  |
|                             | M8 / Ø12    |  |                     |  |  |  |  |
|                             | M10 / Ø16   |  | EO 01 16 210        |  |  |  |  |
|                             | M12 / Ø18   |  | EO 01 18 210        |  |  |  |  |
|                             | M16 / Ø24   |  | EO 01 24 210        |  |  |  |  |
| Blowing pump                |             |  |                     |  |  |  |  |
| Item code: DW 01 00 001     |             |  |                     |  |  |  |  |
| Tecfi HVE Rock Intended use |             |  | Annex B3            |  |  |  |  |
| Cleaning and setting tools  |             |  |                     |  |  |  |  |



|  | tion sequence HVE01   |          |  |  |  |  |  |
|--|---|----------|--|--|--|--|--|
| Installa   | tion sequence HVE02   | Tinst    |  |  |  |  |  |
|  |   |          |  |  |  |  |  |
|  | tion sequence HVE03   |          |  |  |  |  |  |
| installa   |   |          |  |  |  |  |  |
| Step 1   | Drill a hole into the concrete in rotary plus hammer mode             |          |  |  |  |  |  |
| Step 2   | Step 2 Remove the dust into the hole using a brush and a blowing pump |          |  |  |  |  |  |
| Step 3     Place the fixture and hammer the anchor in the drill hole |   |          |  |  |  |  |  |
| Step 4   | Apply the required torque moment                                      |          |  |  |  |  |  |
|  |   |          |  |  |  |  |  |
| Tecfi HV   |   |          |  |  |  |  |  |
| ntended  | <b>use</b><br>n instructions  | Annex B4 |  |  |  |  |  |
| installatio  |   |          |  |  |  |  |  |



| Table C1: Performances for                                  | r design  | method A (te                  | ension) |           |           |            |         |         |
|---|---|-------------------------------|---------|-----------|-----------|------------|---------|---------|
| Type of anchor / Size                                       |   |                               |         | HVE M6    | HVE M8    | HVE M10    | HVE M12 | HVE M16 |
| Steel Failure   |   |                               |         |           |           |            |         |         |
| Characteristic Resistance                                   |   | $N_{Rk,s} = N_{Rk,s,seis,C1}$ | [kN]    | 16        | 29        | 46         | 67      | 125     |
| Partial safety factor                                       |   | γ <sub>Ms</sub> <sup>1</sup>  |         |           |           | 1,5        |         |         |
| Pull-out failure  | I   |                               |         |           |           |            |         |         |
| Effective embedment depth                                   |   | h <sub>ef</sub>               | [mm]    | 55        | 60        | 70         | 90      | 105     |
| Characteristic Resistance in uncracked                      | 1   |                               |         | 10        | 10        | 20         | 25      | 45      |
| concrete C20/25   |   | N                             | [LN]    | 16        | 16        | 20         | 35      | 45      |
| Characteristic Resistance in cracked                        |   | N <sub>Rk,p</sub>             | [kN]    | 5         | 6         | 16         | 25      | 35      |
| concrete C20/25   |   |                               |         | 5         | 0         | 10         | 25      | 35      |
| Characteristic Resistance for seismic                       |   | N <sub>Rk,p,seis,C1</sub>     | [kN]    | 5         | 4,2       | 14,4       | 25      | 35      |
| performance category C1                                     |   | • RK, p, seis, CI             |         |           | .,_       |            |         |         |
| Increasing factors for N <sub>Rk,p</sub> for cracked        | and   |                               | C30/37  |           |           | 1,22       |         |         |
| uncracked concrete  |   | $\Psi_{c}$                    | C40/50  |           |           | 1,41       |         |         |
|   |   |                               | C50/60  |           |           | 1,55       |         |         |
| Installation safety factor                                  |   | $\gamma_2 = \gamma_{inst}$    |         |           |           | 1,0        |         |         |
| Concrete cone failure and splitting fai                     | llure   | -                             | [ ]     |           | 62        | 70         | 60      | 405     |
| Effective embedment depth                                   |   | h <sub>ef</sub>               | [mm]    | 55        | 60        | 70         | 90      | 105     |
| Spacing   |   | S <sub>cr,N</sub>             | [mm]    | 165<br>85 | 180<br>90 | 210<br>105 | 270     | 315     |
| Edge distance   |   | C <sub>cr,N</sub>             | [mm]    |           |           |            | 135     | 160     |
| Spacing(splitting)  |   | S <sub>cr,sp</sub>            | [mm]    | 220       | 320       | 240        | 370     | 390     |
| Edge distance (splitting)<br>Factor for uncracked concrete, |   | C <sub>cr,sp</sub>            | [mm]    | 110       | 160       | 120        | 185     | 195     |
| acc. CEN/TS 1992-4  |   | <b>k</b> <sub>ucr</sub>       |         |           |           | 10,1       |         |         |
| Factor for cracked concrete,                                |   |                               |         |           |           |            |         |         |
| acc. CEN/TS 1992-4  |   | k <sub>cr</sub>               |         |           |           | 7,2        |         |         |
| Installation safety factor                                  |   | $\gamma_2 = \gamma_{inst}$    |         |           |           | 1,0        |         |         |
| <sup>1)</sup> In absence of other national regulations.     |   | 12 11150                      |         |           |           | ,          |         |         |
| Table C2: Performances for                                  | r design  | method A (sh                  | near)   |           |           |            |         |         |
| Type of anchor / Size                                       |   |                               | HVE M   | 6 HVE     | M8 HV     | 'E M10   F | IVE M12 | HVE M16 |
| Steel Failure without level arm                             |   |                               |         |           |           |            |         |         |
| Characteristic Resistance                                   | V <sub>Rk,s</sub>   | [kN]                          | 16      | 25        | 5         | 43         | 58      | 107     |
| Characteristic Resistance for seismic                       |   |                               | 11.4    | 1-        | ,         | 20         | 42.5    | 06.2    |
| performance category C1                                     | $V_{Rk,s,seis}$ ,   | .c1 [kN]                      | 11,4    | 17        | /         | 28         | 43,5    | 96,3    |
| Partial safety factor                                       | γ <sub>Ms</sub> 1)  |                               |         |           |           | 1,45       |         |         |
| Steel Failure with level arm                                |   |                               |         |           |           |            |         |         |
| Characteristic bending moment                               | M <sup>0</sup> <sub>Rk,s</sub><br>γ <sub>Ms</sub> <sup>1)</sup> | [Nm]                          | 12      | 30        | )         | 60         | 105     | 266     |
| Partial safety factor                                       | γ <sub>Ms</sub> 1)  |                               |         |           |           | 1,45       |         |         |
| Concete pryout failure                                      |   |                               |         |           |           |            |         |         |
| Effective embedmen depth                                    | h <sub>ef</sub>   | [mm]                          | 55      | 60        | )         | 70         | 90      | 105     |
| Factor for pryout failure                                   | k = k <sub>3</sub>  |                               | 1       | 2         |           | 2          | 2       | 2       |
| Installation safety factor                                  | $\gamma_2 = \gamma_{ins}$                                       | st                            |         |           |           | 1,0        |         |         |
| Concrete edge failure                                       |   |                               |         |           |           |            |         |         |
| Effective achorage legth                                    | $I_{ef}$  | [mm]                          | 55      | 60        | )         | 70         | 90      | 105     |
| Effective external diameter anchor                          | d <sub>nom</sub>  | [mm]                          | 10      | 12        | 2         | 16         | 18      | 24      |
| Installation safety factor                                  | $\gamma_2 = \gamma_{in}$  |                               |         |           |           | 1,0        |         |         |
| <sup>1)</sup> In absence of other national regulations      | 5.  |                               |         |           |           |            |         |         |
| Tecfi HVE Rock  |   |                               |         |           |           |            |         |         |
| Performances  |   |                               |         |           |           | ۰          | ov C1   |         |
| Characteristic resistance to tens                           | ion load  | ds under static               | and qu  | asi-      |           | ANN        | ex C1   |         |
| static actions and seismic perfor                           |   |                               |         |           |           |            |         |         |
| static actions and seisinic perior                          | mance   | Category CI                   |         |           |           |            |         |         |



| Duration of fire resistance = 30m | iin, anchor type                        | HVE   | M6          | M8            | M10                 | M12        | M16                        |
|-----------------------------------|---|-------|-------------|---------------|---------------------|------------|----------------------------|
| Steel Failure                     |   |       |             |               |                     |            |                            |
| Characteristic Resistance         | N <sub>Rk,s,fi,30</sub>                 | [kN]  | 0,2         | 0,4           | 0,9                 | 1,7        | 3,1                        |
| Pull-out failure                  |   |       |             |               |                     |            |                            |
| Characteristic Resistance in      | Net and                                 | [kN]  | 1,3         | 1,5           | 4,0                 | 6,3        | 8,8                        |
| concrete C20/25 to C50/60         | N <sub>Rk,p,fi,30</sub>                 |       | 1,5         | 1,5           | 4,0                 | 0,5        | 0,0                        |
| Concrete cone failure             |   |       |             |               |                     |            |                            |
| Characteristic Resistance in      | N <sup>0</sup> <sub>Rk,c,fi,30</sub>    | [kN]  | 4,0         | 5,0           | 7,4                 | 13,8       | 20,3                       |
| concrete C20/25 to C50/60         |   |       | 4,0         | 5,0           | ,,-                 | 13,0       | 20,5                       |
| Duration of fire resistance = 60m | in, anchor type                         | HVE   | M6          | M8            | M10                 | M12        | M16                        |
| Steel Failure                     |   |       |             |               |                     |            |                            |
| Characteristic Resistance         | N <sub>Rk,s,fi,60</sub>                 | [kN]  | 0,2         | 0,3           | 0,8                 | 1,3        | 2,4                        |
| Pull-out failure                  |   |       |             |               |                     |            |                            |
| Characteristic Resistance in      | Nation                                  | [kN]  | 1,3         | 1,5           | 4,0                 | 6,3        | 8,8                        |
| concrete C20/25 to C50/60         | N <sub>Rk,p,fi,60</sub>                 |       | 1,5         | 1,5           | 4,0                 | 0,5        | 0,0                        |
| Concrete cone failure             |   |       |             | 1             |                     | -          | 1                          |
| Characteristic Resistance in      | N <sup>0</sup> <sub>Rk,c,fi,60</sub>    | [kN]  | 4,0         | 5,0           | 7,4                 | 13,8       | 20,3                       |
| concrete C20/25 to C50/60         |   |       | 1,0         | 3,0           | -,,                 | 10,0       | 20,0                       |
| Duration of fire resistance = 90m | M6                                      | M8    | M10         | M12           | M16                 |            |                            |
| Steel Failure                     |   |       |             |               |                     |            |                            |
| Characteristic Resistance         | N <sub>Rk,s,fi,90</sub>                 | [kN]  | 0,1         | 0,3           | 0,6                 | 1,1        | 2,0                        |
| Pull-out failure                  |   |       |             |               |                     |            |                            |
| Characteristic Resistance in      | N <sub>Rk,p,fi,90</sub>                 | [kN]  | 1,3         | 1,5           | 4,0                 | 6,3        | 8,8                        |
| concrete C20/25 to C50/60         | Rk,p,fi,90                              |       | 1,5         | 1,5           | 4,0                 | 0,5        | 0,0                        |
| Concrete cone failure             |   |       |             |               |                     |            |                            |
| Characteristic Resistance in      | N <sup>0</sup> <sub>Rk,c,fi,90</sub>    | [kN]  | 4,0         | 5,0           | 7,4                 | 13,8       | 20,8                       |
| concrete C20/25 to C50/60         |   |       | -           | - , -         |                     |            | /-                         |
| Duration of fire resistance = 120 | min, anchor type                        | e HVE | M6          | M8            | M10                 | M12        | M16                        |
| Steel Failure                     |   |       |             | 1             |                     | 1          |                            |
| Characteristic Resistance         | N <sub>Rk,s,fi,120</sub>                | [kN]  | 0,1         | 0,2           | 0,5                 | 0,8        | 1,6                        |
| Pull-out failure                  |   |       | -           | T             | 1                   | 1          |                            |
| Characteristic Resistance in      | N <sub>Rk,p,fi,120</sub>                | [kN]  | 1,0         | 1,2           | 3,2                 | 5,0        | 7,0                        |
| concrete C20/25 to C50/60         | ••••••••••••••••••••••••••••••••••••••• | []    |             |               | -,-                 |            | .,.                        |
| Concrete cone failure             |   |       |             | 1             |                     | 1          |                            |
| Characteristic Resistance in      | N <sup>0</sup> <sub>Rk,c,fi,120</sub>   | [kN]  | 3,2         | 4,0           | 5,9                 | 11,1       | 16,3                       |
| concrete C20/25 to C50/60         |   |       |             | ,             |                     | ,          | , .                        |
| Spacing                           | S <sub>cr,N</sub>                       |       |             |               | 4 x h <sub>ef</sub> |            |                            |
|                                   | S <sub>min</sub>                        |       | 55          | 110           | 80                  | 135        | 130                        |
|                                   | C <sub>cr,N</sub>                       | [mm]  |             |               | 2 x h <sub>ef</sub> |            |                            |
| Edge distance                     | <b>C</b> .                              |       |             |               | comes from r        |            |                            |
|                                   | C <sub>min</sub>                        |       | edge distan | ce of the and | hor has to be       | ≥ 300mm or | $\geq 2 \text{ x } h_{ef}$ |

| Tecfi HVE Rock  |          |
|---|----------|
| Performances  | Annex C2 |
| Characteristic values for tension loads under fire exposure |          |



| Duration of fire resistance = 30min, anche                                   | M8  | M10                      | M12   | M16          |            |         |     |
|--|---|--------------------------|---|--------------|------------|---------|-----|
| Shear load without lever arm   |   |                          |   |              |            |         |     |
| Characteristic resistance  | V <sub>Rk,s,fi,30</sub>                                 | [kN]                     | 0,3   | 0,5          | 1,2        | 2,1     | 3,9 |
| Shear load with lever arm  |   |                          |   |              |            |         |     |
| Characteristic bending resistance  | M <sup>0</sup> <sub>Rk,s,fi,30</sub>                    | [Nm]                     | 0,2   | 0,4          | 1,1        | 2,6     | 6,7 |
| Duration of fire resistance = 60min, anch                                    | ration of fire resistance = 60min, anchor type HVE M6 M |                          |   |              |            |         | M16 |
| Shear load without lever arm   | 1   | 1 1                      |   |              | 1          | 1       |     |
| Characteristic resistance  | V <sub>Rk,s,fi,60</sub>                                 | [kN]                     | 0,3   | 0,4          | 1,0        | 1,6     | 2,9 |
| Shear load with lever arm  |   | 1                        |   |              | 1          |         |     |
| Characteristic bending resistance  | M <sup>0</sup> <sub>Rk,s,fi,60</sub>                    | [Nm]                     | 0,1   | 0,3          | 1,0        | 2,0     | 5,0 |
| Duration of fire resistance = 90min, anch                                    | or type HVE   |                          | M6  | M8           | M10        | M12     | M16 |
| Shear load without lever arm   |   |                          |   |              |            |         |     |
| Characteristic resi stance   | V <sub>Rk,s,fi,90</sub>                                 | [kN]                     | 0,2   | 0,3          | 0,8        | 1,4     | 2,5 |
| Shear load with lever arm  |   | 1                        |   |              |            |         |     |
| Characteristic bending resistance  | M <sup>0</sup> <sub>Rk,s,fi,90</sub>                    | [Nm]                     | 0,1   | 0,3          | 0,8        | 1,7     | 4,3 |
| Duration of fire resistance = 120min, and                                    | nor type HVE  |                          | M6  | M8           | M10        | M12     | M16 |
| Shear load without lever arm   | 1   |                          |   |              |            | 1       |     |
| Characteristic resistance  | V <sub>Rk,s,fi,120</sub>                                | [kN]                     | 0,2   | 0,2          | 0,6        | 1,0     | 1,9 |
| Shear load with lever arm  | 1   | 1 1                      |   |              | 1          | 1       |     |
| Characteristic bending resistance  | M <sup>0</sup> <sub>Rk,s,fi,120</sub>                   | [Nm]                     | 0   | 0,2          | 0,6        | 1,3     | 3,3 |
| Concrete pryout failure  |   |                          |   |              |            |         |     |
| The characteristic resistance $V_{\text{rk,cp,fi,Ri}}$ in co                 | ncrete C20/2  | 5 to C50                 | /60 is detern                                 | nined by:    |            |         |     |
| $V_{Rk,c,fi(90)} = k \times N_{Rk,c,fi(90)} (\le R90)$ and $V_{Rk,c,fi(90)}$ | 120) = k x N <sub>Rk,c</sub>                            | , <sub>fi(120)</sub> (up | o to R120)                                    |              |            |         |     |
| Concrete edge failure  |   |                          |   |              |            |         |     |
| The characteristic resistance $V_{rk,cp,fi,Ri}$ in co                        |   |                          |   |              |            |         |     |
| $V^{0}_{Rk,c,fi(90)} = 0,25 \times V^{0}_{Rk,c}$ (R30, R60, R90) ar          | nd <b>V<sup>0</sup><sub>Rk,c,fi(120)</sub></b>          | ) = <b>0,20</b>          | <b>( V<sup>0</sup><sub>Rk,c</sub> (</b> R120) | ) with       |            |         |     |
| $V^0_{_{Rk,c}}$ as an initial value of the characteristi                     | c resistance o  | of a sing                | e anchor in c                                 | racked conci | ete C20/25 |         |     |
|  |   |                          |   |              |            |         |     |
|  |   |                          |   |              |            |         |     |
|  |   |                          |   |              |            |         |     |
|  |   |                          |   |              |            |         |     |
|  |   |                          |   |              |            |         |     |
|  |   |                          |   |              |            |         |     |
|  |   |                          |   |              |            |         |     |
|  |   |                          |   |              |            |         |     |
|  |   |                          |   |              |            |         |     |
|  |   |                          |   |              |            |         |     |
|  |   |                          |   |              |            |         |     |
| ecfi HVE Rock  |   |                          |   |              |            |         |     |
| Γecfi HVE Rock<br>Performances   |   |                          |   |              | Δ          | nnex C3 |     |



| Table C5 : Displacemen   | ts                    |      |     |      |      |      |      |
|--|-----------------------|------|-----|------|------|------|------|
| Tension loads in cracked and unc                               | racked conci          | ete  | M6  | M8   | M10  | M12  | M16  |
| Service tension load in<br>uncracked concrete C20/25           | Ν                     | [kN] | 7,6 | 7,6  | 9,5  | 16,7 | 21,4 |
| Dicplacements  | $\delta_{\text{NO}}$  | [mm] | 1,3 | 1,5  | 1,0  | 1,3  | 1,8  |
| Displacements -  | $\delta_{N^\infty}$   | [mm] | 1,3 | 1,5  | 1,0  | 1,3  | 1,8  |
| Service tension load in cracked concrete C20/25                | Ν                     | [kN] | 2,4 | 2,9  | 7,6  | 11,9 | 16,7 |
| Displacements -  | $\delta_{\text{NO}}$  | [mm] | 1,0 | 0,7  | 1,0  | 1,2  | 1,5  |
| Displacements  | $\delta_{N^\infty}$   | [mm] | 1,6 | 1,3  | 1,6  | 1,7  | 1,5  |
| Shear loads in cracked and uncra                               | cked concret          | e    | M6  | M8   | M10  | M12  | M16  |
| Service shear load in cracked<br>and uncracked concrete C20/25 | V                     | [kN] | 7,7 | 12,3 | 21,0 | 23,3 | 52,5 |
| Dicplacements  | $\delta_{V0}$         | [mm] | 2,4 | 2,6  | 2,5  | 3,0  | 4,0  |
| Displacements -  | $\delta_{V^{\infty}}$ | [mm] | 3,6 | 3,9  | 3,8  | 4,5  | 6,0  |

| Tecfi HVE Rock |          |
|----------------|----------|
| Performances   | Annex C4 |
| Displacements  |          |